


Test Report	Sample No:1599979447	Page 1 of 1
Test Component Description : Aluminium sheet with printed labels Sample B: B/1, 2, 3, 4, 5, 6, 7		
Size:- Not Applicable	Part No:- Not Applicable	
Test Specification:- Light fastening (Weathering) test as per IS:2932, SAE J 1960 & PVT/(CIRT-CSD 3348)		

Sr. No	Test Description	Actual test results
--------	------------------	---------------------

1	<u>Accelerated weathering test :</u> (21 days), Irradiance:0.55w/m ²	B1	B2	B3	B4	B5	B6	B7
	a) Gloss retention % @ 60°	91.49	86.41	88.50	96.00	91.95	90.49	88.26
	b) Colour rating	08	06 C	07 C	07 C	05 C	09	08
	c) Freedom from checking, rating	09	07	09	10	09	10	10
	d) Freedom from cracking, rating	10	10	10	10	10	10	10
	e) Freedom from chalking, rating	09	09	10	10	10	10	10
	f) Freedom from flaking , rating	10	10	10	10	10	10	10
	g) Freedom from spotting, rating	10	10	10	10	10	10	10
	h) Freedom from blistering & corrosion , rating	10	10	10	10	10	10	10

ASSESSMENT :- Only test results are reported as per the requirement of M/S Durasign Brand Solution Pvt. Ltd. vide Letter Ref. No. 2K15/07/175 dated 21/ 07/ 2015 .



I.M.Yelurkar, Scientist 'B'
Scientist – Environmental Lab.

CENTRAL INSTITUTE OF ROAD TRANSPORT

(A unit of the Association of State Road Transport Undertakings)
POST BOX No. 1897, PUNE-NASIK ROAD, BHOSARI, PUNE-411 026. INDIA
Phone -(0091)-(020) 67345300 (30 Channels) Fax : (+91) 20 67345407
Email : td@cirtindia.com Website : http://www.cirtindia.com

No. : A 89100



TEST REPORT

- This Test Report is in respect of the particular item/material actually tested and to the specific tests carried out as detailed in the Test Report.
- This Test Report or the information given therein is not to be quoted/reproduced in full or part, and not to be used for publicity or advertisement purpose without the written permission of the Director, CIRT.
- The Institute does not take any responsibility for preserving the test item / sample / component for more than one month from the date of Test Report.
- All disputes or any nature related to this Test Report shall lie within the jurisdiction of the Pune only.

Report No. : **ED/15-16/1599979447/Q1395**

To

Durasign brand solution pvt.ltd.
Gat No.1571, Shelar Vasti,
Dehu-Alandi Rd, Chikhali,
Maharashtra 411062

28 AUG 2015


1. Nomenclature and Part No.	ALUMINIUM SHEET WITH PRINTED LABELS SAMPLE B: B/1, 2, 3, 4, 5, 6, 7
2. Sample Regn. No. /Code No.	P15882/ 1599979447
3. No. /Quantity of Sample	2 NOS
4. Sample Supplied by and Reference No.	DURASIGN BRAND SOLUTION PVT. LTD PUNE 2K15/07/175 Dtd. 21/07/2015
5. Name of Manufacturer	DURASIGN BRAND SOLUTION PVT. LTD
Marking	NO MARKING
6. Your Code No.	
7. Date of receipt of sample	22/07/2015
8. Date of Technical clearance	30/07/2015
9. Date of Clearance of Doc.	30/07/2015
10. Specifications	LIGHT FASTENING (WEATHERING) TEST AS PER IS:2932, SAE J 1960 & PVT/(CIRT-CSD 3348)
11. Identification of method used	As described in specification
12. Condition of Item	Good
13. Date of Completion of Test	24/08/2015
14. Test Results	As per Annexure "A" (Enclosed)

Assessment of Test Results

The test results are reported as mentioned in Annexure-A.

Disclaimer:- CIRT issues Type Approval Certificate / Test Certificate / Extension Report for vehicles / components / parts / assemblies etc. based on the documents produced / submitted by the customer and on this basis, testing is carried out and the certificate is issued. CIRT is in no way responsible for any misuse of copying of any design / type / system in connection with entire vehicle / components / parts and assemblies. Breach of any statutory provision of Indian laws or laws of other countries, will be the sole responsibility of the customer and CIRT shall not be liable for any claims or damages, made by the party, whatsoever, the customer shall alone be liable for the same, and undertakes to indemnify CIRT in this regard. The CIRT has the right to initiate cancellation / withdrawal of the certificate issued, in case of any fraud, misrepresentation, when it surfaces and comes in the knowledge of CIRT. All disputes of any nature are subject to Pune (India) jurisdiction only. CIRT does not undertake any responsibility in respect of field performance of the vehicle component as well as issues arising during the operation. This Test Certificate / Extension Report or the information given therein is not to be quoted / reproduced in full or part and not to be used for publicity or advertisement purpose without the written permission of the the Director, CIRT.

1


**Mr. N.R. Kachare, Scientist E,
Head-Engineering Division**

CENTRAL INSTITUTE OF ROAD TRANSPORT

(A unit of the Association of State Road Transport Undertakings)

POST BOX No. 1897, PUNE-NASIK ROAD, BHOSARI, PUNE-411 026. INDIA

Phone -(0091)-(020) 67345300 (30 Channels) Fax : (+91) 20 67345407

Email : td@cirtindia.com

Website : http://www.cirtindia.com

No. : A

35274

B



1



2




3




4



5

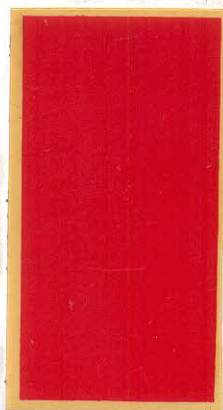

6

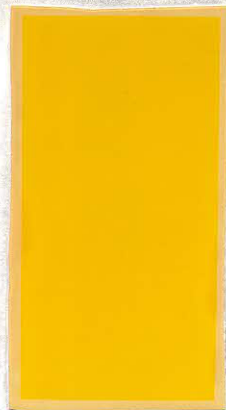

7

B



1




2



3



4

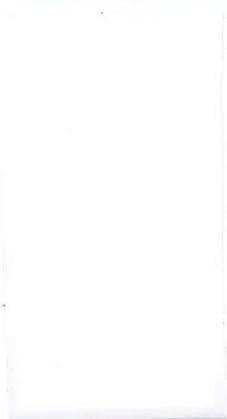

5



6



7